

Geosynthetics → geotextiles - types - functions
properties and applications - Geogrids

Geomembrane and gabions - properties and applications.

Types of Geosynthetics : —

1. Geospacers : —

These geospacers are the impermeable spacers used in tin chains only.

2. Geoproducts : —

These products are obtained from natural fibres. Geospacers and metallic soil reinforcement.

3. Geosynthetic

It Generally consists of geotextile and geomembrane. Mostly geotextile products are used. These should be manmade fibres.

4. Geofabrics : —

These are Geotextile products such as planar flat sheet geotextile in these geotextile mats are not used.

5. Geocomposites : —

It Generally consists of more than one Geo product.

6. Geogrids : —

Geogrids also consists of Geotextile products.

If the geotextile products are made up of large rectangular apertures, then they are commonly known as Geotextile grids and non-rectangular apertures. then they are commonly known as Geotextile nets.

(*) Geotextiles : —


Geotextile is a porous textile material manufactured from synthetic material such as polypropylene, polyester, polyethane etc., these are used to improve or modify soil or rock behaviour.

Geotextiles are of types — woven Geotextiles
+ Non woven Geotextiles.

Functions of Geotextiles : —

1. Fluid Transmission : — (drainage function)


A Geotextile can collect a liquid and convey it along its own plane, thus providing fluid transmission. It is also called drainage function.

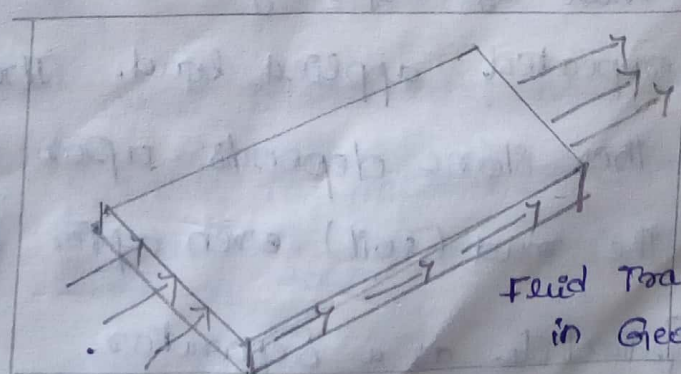

Fluid Transmitted
in Geogrids

②. Filtration:


The function of filtration involves the movement of water normal to the plane of Geotextile while preventing soil particles from being carried away from liquid current.

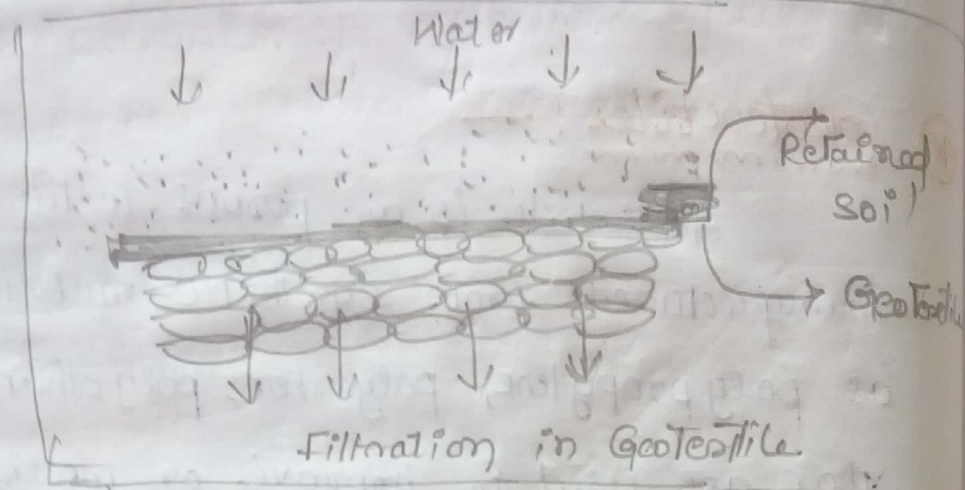

③ Separation with Geotextile:-


- As a separator in foundation bed
- As a separator in subgrade and sub base.

When stone is placed in mud, the stone sinks into it and only mud can be seen. If a Geotextile is placed between the mud and stone, it prevents the stone from sinking into the mud by self weight or under the action of repeated applied load. The rate of sinking of the stone depends upon the proportion of the mud (soil) even after providing Geotextile as a separator.

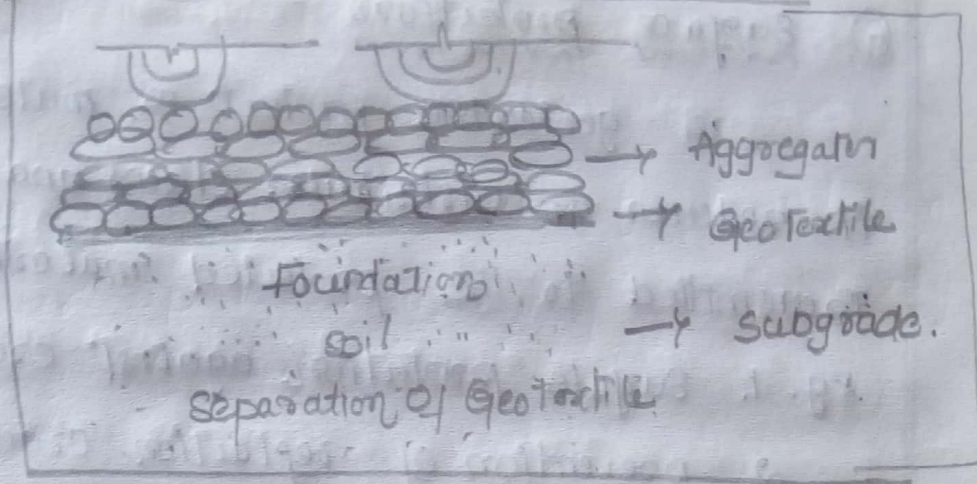

④ Reinforcement : —

Geotextile being a high Tensile strength material can complement those material which are weak in Tension. Those soils which are poor in Tension and good in Compression or other disjointed material can strengthen by reinforcing with geotextiles.

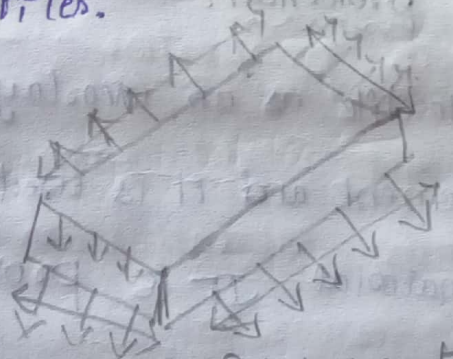

⑤ Moisture Barrier : —


By using a fabric that does not facilitate both cross plane and in plan flow, it should be possible to impend or minimize effectively the flow of water as well as the movement of water vapor.

⑥ Surface protection :-

is geotextile protect a material when it reduces or distributes stress and strains transmitted to the protected material.

eg. 1. surface protection against erosion

2 prevention of reflection cracking on asphalt pavement overlays.

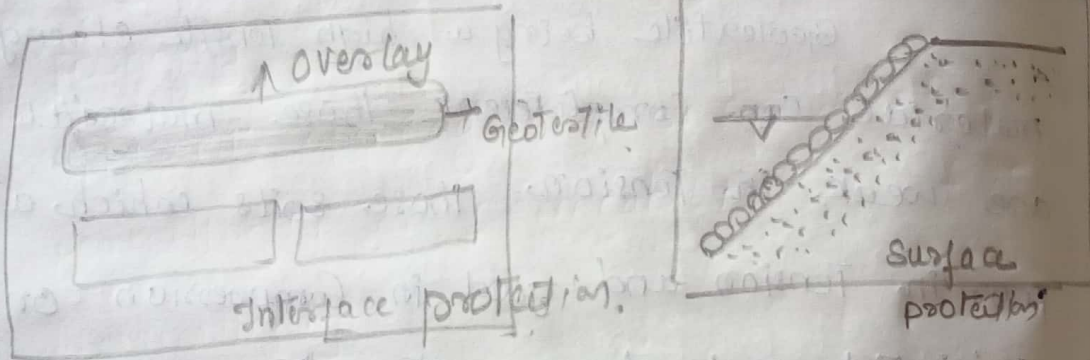

⑦ Interface protection :-

Geotextile as an overlay material in Concrete pavement and it is used as interface protection material. It is provided in b/w the BT and bitumen coarse material.

8. Geosynthesis and Tensile member :-

In case of earth retaining structures

Geotextile can be used as Tensile members.

In some of the above cases, Geotextile of the serve more than one purpose.

* Physical properties of Geotextiles:-

1. Physical properties:-

(a) Physical properties:-

(a) Specific Gravity:- defined as ratio of materials unit volume weight (without voids) to that of distilled water.

sp. gravity values for polymeric material that are made into geotextiles.

Steel = 7.87

Soil rock = 2.9-2.4

Glass = 2.54

Cotton = 1.55

polyvinyl chloride = 1.69

Polyster = 1.38-1.22

Nylon = 1.14 to 1.05

polyethylene = 0.96-0.9

polypropylene = 0.91

(b). Mass per unit Area:-

It is an important property mass should be measured to nearest 0.017 of total specimen mass

(c) Thickness:- It is measured as distance

b/w upper & lower surface of the fabric.

Thickness commonly used range from 0.25-75mm

2. Mechanical properties:-

(a) Compressibility:- For most Geotextiles Compressibility is relatively low.

- (b) Tensile strength.
- (c) Confined Tensile strength
- (d) Seam strength (Joining the line at two edges)
- (e) Burst strength (Break with force)

Burst occurs due to a gas or liquid pressure acting on a membrane.

(3) Hydraulic properties : —

porosity,

apparent opening size or equivalent opening

permittivity or permeability size

Transmittivity

Percent open Area.

(4) Endurance properties : —

1. ultraviolet light exposure
2. Radio active degradation
3. Biological degradation
4. chemical "

5. Thermal Behaviour.

(*) Application of Geotextiles

The geotextile applications are used every where and combined, adopted to different circumstances.

→ Geotextile, based on versatile is used

they are combined with many Tradition and new building materials

→ The Various application Areas of Geotextile used as.

(1) Rail Roads: — The purpose of geotextile is to distribute the load on subgrade and prevents from ballast Contaminations.

(2) Shore protection: —

protects from sand migration and from erosion

(3) Embankments: — It Generally improves stability

(4) Natural slopes: —

The slopes protect from the erosion and soil reinforcement

* Geo Grids: —

.. Geogrid consisting of Connected parallel sets of Tensile strips with apertures of sufficient size to allow strike through of surrounding soil, stone or other geotechnical material. Geogrids are matrix like material with large open spaces called apertures. which are typically 10-100 mm b/w ribs.


There are 3 Types of Geogrids.

1. Biaxial Geogrids: — Improve the structural integrity of roadways & distributing load force.

also used for road construction on stable ~~gas~~ sub graded to reduce the aggregate thickness requirements.

2. uniaxial Geogrids: — In Grade separation applications, uniaxial Geogrid are used to help soils stand at virtually wide variety of facing elements in retaining wall and application to produce desired structural or esthetic condition for any project.

3. Triaxial Geogrid: — Triaxial is a stationary new geogrid product from Tensor. The Triangular structure of Triaxial geogrid, coupled with the increased rib thickness & junction efficiency, greatly improved aggregate interlock & confinement. Triaxial geogrid can reduce aggregate base/subbase requirements by 25% to 50%.

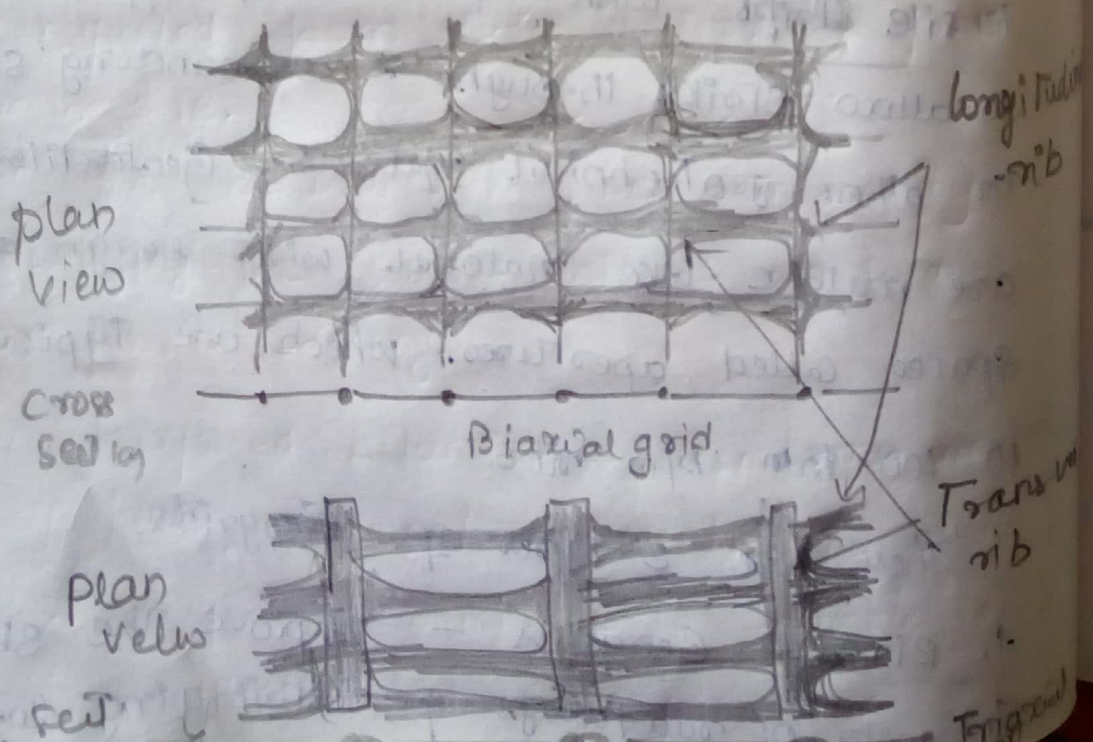

Functions of Geogrids :-

similar to geotextiles. But they do not serve the purpose of filter or a moisture barrier due to their large opening size.

→ These are applied in rolls 1 to 3 m wide due to their large opening size.

→ These are used between layers of wall sections such as concrete cells or concrete blocks to anchor the walls and to reduce earth pressure on wall itself.

→ Geogrid stabilise soil mass

→ Much higher loads carried by soil stabilise.

Uses of Geogrids :-

→ Erosion Control. → Bearing Capacity Improvement

→ To repair slope failures & land slides

→ As Intersects b/w Geotextiles

→ Beneath surcharge fills.

→ Beneath balast in rail road construction

→ To reinforce designated rock sections

→ To reinforce landfills to allow for lateral Expansion.

→ as Asphalt reinforcement in pavements

* Geo Membranes : —

Membrane Geosynthetics are generally referred to as Geomembranes which are thin two-dimensional sheets of material with a very low permeability. These are flexible material and can be strengthened with a fabric or film. Geomembranes are only subject to a small amount of seepage as a result of permeation.

→ For all practical purposes they may be considered to be impermeable to both gases and fluids.

→ Geomembranes are manufactured from synthetic (thermoplastic) materials such as HDPE, LLDPE, PVC, CPE etc for bitumen product such as ECB.

→ There is a distinction between membranes manufactured ~~from~~ in the factory or fabricated on the site.

→ The membranes may be reinforced by spraying the viscous material on to a membrane or fabric backing.

→ Reinforced bituminous membranes are built up from different elements. The basis of the reinforced membrane is ~~subgrade~~ ^{subgrade} for of polyamide fabric or polyester membrane.

soaked in the bituminous mixture.

Applications of Geomembranes :-

Geomembranes have been used in following environmental, geotechnical, hydraulic, Transportation & private development applications.

- As liner for potable water
- As liner for waste liquids
- As liner for radioactive or hazardous waste liquid, Secondary Containment of underground storage Tanks, agricultural industry and various waste conveyance Canals.
- As various Cor) Caps for solid waste Landfills, Power plants, coal ash
- As waterproofing facing of earth & rock fill dams, masonry dams, & Concrete dams
- To Contain & Transport liquid in Tanks
- To Control expansive soils, frost-susceptible soils.
- To prevent Infiltration of water in Sensitive area.

Geosynthetics unit-5

Geosynthetics are artificial fabrics used in conjunction with soil or rock as an integral part of a man-made project. Natural or Artificial products that is used along with soil in geotechnical constructions.

Natural occurring geotextile: Coir, jute etc

Artificial Occurring geotextile: polymers ^(or) and metallic etc.

Why geosynthetics?

- They have entirely changed the way geotechnical engineering is practised.
- Innovative Solutions to solve difficult problems economically.
- It enables the use of local materials.
- Unskilled labor can be employed.
- Installation does not require heavy machinery.

Types of geotextiles GeoSynthetics

- ① Geotextiles
- ② Geo grids
- ③ Geo nets
- ④ Geomembranes
- ⑤ Geo Cells.
- ⑥ Geocomposite
- ⑦ PVD (prefabricated Vertical drains)
- ⑧ GCL (Geosynthetic Clay liners)

Geotextiles:

It can be simply defined as "a textile material used in a soil environment" and includes woven and non woven polymeric materials and natural materials such as jute, manufacture using textile processes.

Polymers: Geotextiles are usually made from one of the

4 Synthetic polymers

① polyamide

② polyester

③ polyethylene

④ polypropylene.

Polyamide: The production process and the material properties are influenced by the use of

Various additives such as

→ Viscosity Stabilisers which controls the degree of polymerisation during process.

→ Ageing Inhibitors which protects the polymers against the ageing due to light or thermo-oxidation.

→ Colouring i.e Carbon black which also has the advantage of increasing the stability of polyamides.

(2)

polyester: Additives used in the production of polyester are.

- (a) Catalysts which increases the speed of polymerisation.
- (b) phosphoric compounds which reduces thermal degradation during processing in the molten stage.
- (c) Ageing inhibitors which increases UV resistance.

polyethylene: 2 main groups are identified

- low density polyethylene [density $920 - 930 \text{ kg/m}^3$]
- high density polyethylene [density $940 - 960 \text{ kg/m}^3$].

low density polyethylene is produced at high temperatures pressures (upto 300 MN/m^2)

high density polyethylene is produced at low pressures (4 MN/m^2) and low temperatures.

polypropylene: (1) The polymerisation of propylene monomers in the presence of specific ~~gravity~~ catalysts produces the crystalline thermoplastic polypropylene (2) It is very susceptible to oxidation and additives are required to protect against ageing.

(3) other additives are also used to improve

thermal stability, UV resistance and underwater resistance.

Types of geotextiles:

Woven Geotextiles:

Nonwoven Geotextiles:


Woven Geotextiles: (1) These were developed from synthetic or natural fibers using weaving techniques.

(2) The ^{woven} weaving process gives these geotextiles an appearance of two sets of parallel threads interlaced at right angles.

(3) 'Warp' runs along the length of the looms

(4) ~~'Weft'~~

(4) 'Weft' runs along transverse direction across loom.

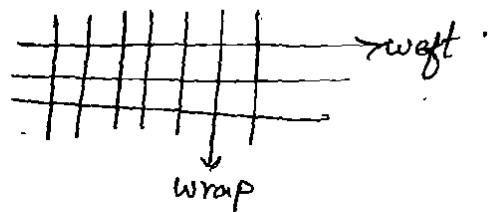

(5) The yarn used to produce a woven geotextile may be monofilament (or) multifilament (or) a combination of each type.

(6) The yarn in the warp direction has to

stand the action of the loom's reeds continuously pulling & pushing it apart to make way for the Shuttle which pulls the Weft yarn through.

Non woven geotextiles: These are formed from filaments or ~~fibres~~ fibres arranged at random and bonded together into a planar structure.

The filaments or fibers are first arranged into a loose web, then banded together.

Non woven geotextiles are obtained by following processes:

- ① Thermal bonding: (i) These geotextiles are produced by spraying continuous polymer filaments on to a moving belt which is then passed through heated rollers.
(ii) These rollers compress the layers of loose filaments and cause partial melting of the polymer, leading to the thermal bonding of these

thermally bonded geotextiles tends to be relatively thin.

The random distribution of the filaments results in a wider range of opening sizes than is found in a woven geotextile.

The absence of any preformed orientation of the filaments results in a more isotropic strength compared to wovens.

Mechanical Bonding: (i) These geotextiles are formed by introducing a fibrous web into a machine equipped with groups of specially designed needles.

(ii) While the web is trapped b/w plates, the needles pushed through it and reorientate the fibres so that mechanical bonding is achieved.

(iii) In this process the fabrics obtained have high density, considerable bulk and thick.

Chemical Bonding: (i) They are produced by spraying polymer filaments on to a moving conveyor and then spraying an acrylic resin into or onto the fabric web.

(9)
(ii) After curing or rolling, strong bonds are formed b/w the filaments.


(iii) A forced-air drying operation is required to establish the open pore structure fabrics.

Functions of Geotextiles:

four basic functions of geotextile are

- (i) Separation
- (ii) filtration
- (iii) Drainage.
- (iv) Reinforcement.


Separation: A geotextile placed b/w a fine soil and a coarse material to prevent the two materials from mixing. with the introduction of this barrier the dissimilar materials are each able to function properly.

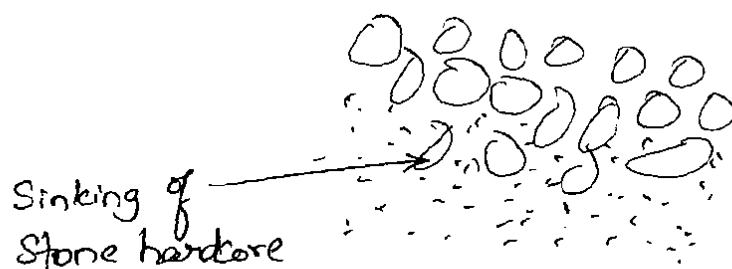

Sinking of Stone hardcore into Subsoil

19


without geotextile

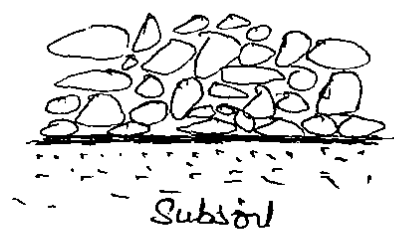

with geotextile.


geotextile separator

filtration: A geotextile placed in contact with a soil, it allows water to pass through while preventing the passage of soil particles. Both adequate permeability and soil retention are required simultaneously over the design life of such application.

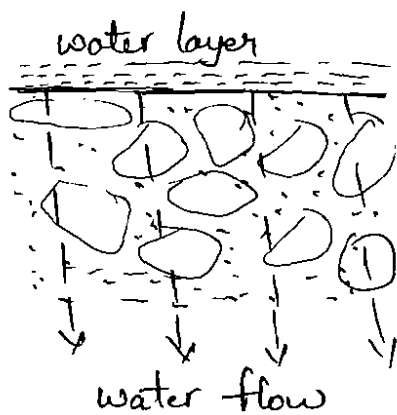

Without Geotextiles

Here fines are ~~carried~~ washed away)

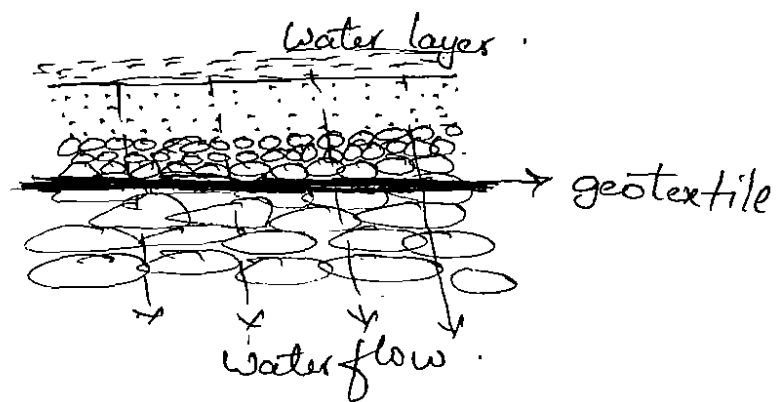

with geotextile


(Here fines are retained).

Drainage: A geotextile collects a liquid and conveys it towards an outlet. All fabrics can provide such a function, but a thin woven fabric obviously has less capacity than a thick needle punched non-woven.

However, the capacity of fabrics is limited &

③
ecocomposites drains have been developed to provide increased capacity.

the flow of water into the drains is controlled by the geotextiles which must also performed as filter function to prevent loss of capacity due to the soil entry into the drain.

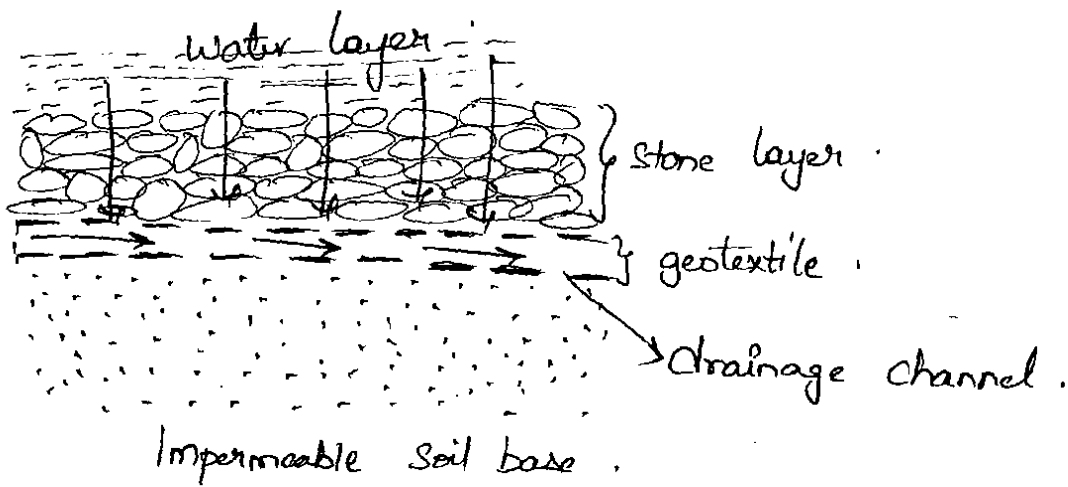

Reinforcement: A geotextile used to improve the mechanical properties of an earth structure by interacting with soil through interface shear.

Properties of Geotextiles:

- ① physical properties.
- ② Mechanical properties.
- ③ Hydraulic properties.

Physical properties:

Mass/unit area: ① The mass per unit area is determined by cutting from a roll a minimum of 10 ~~specimens~~ ^{specimens}, each at least 100 mm^2 , and then weighing the specimens on an accurate balance.

② This test is used to determine quality of ~~geotextile~~ geotextile & helps in identify the material.

③ Cost of material is related to mass/unit area.

Normal thickness/Dimensions: ① normal thickness is determined by placing a sample of geotextile on a plane reference plate and applying a pressure of 2 kN/m^2 through a ~~plus for~~ Circular pressure plate with a c/s area of 2500 mm^2 .

② Vernier gauge measures the thickness b/w pressure plate & reference plate.

③ This test is for determining quality ~~and~~ & Classification of geotextile.

parent pore size distribution by dry sieving:

The pore size distribution of the fabric is determined by sieving dry spherical glass beads for a specified time at a specified frequency of vibration and then measuring the amount retained by the fabric sample.

This test provides information on the pore size distribution which is an important parameter to be used in assessing a geotextile soil filtration capability.

% Open Area determination for woven ~~geo~~ geotextiles:

A small section of the fabric is held within a standard slide cover, inserted into a projector and the magnified image traced on to a sheet of paper. Using planimeter, the magnified open spaces can be measured & expressed as ~~area~~ % of whole area.

- This test is applicable to monofilament woven fabrics.
- This test provides information on pore size openings which data is used for determining soil filtration capacity.

Mechanical properties:

tensile properties using a wide width strip:

A Specimen of the geotextile at least 200mm wide is clamped within the compressive jaws of a tensile testing machine which is capable of applying the loads at a constant rate of strain. During loading a load-strain curve is plotted and from this the max load, breaking load & the Secant modulus at any specified strain may be determined.

This test is useful for quality control & can also be used for design purpose.

puncture strength of geotextiles:

A Specimen of the fabric is clamped, without tension, over a empty cylinder, and a solid steel rod is pushed through the fabric. A load indicator attached to the rod measures the force required to cause rupture.

A CBR (Soil) testing apparatus may be modified for this test.

This test is used to determine fabric resistance against aggregate penetration.

(1)

fabric friction test: This is an adaption of the direct shear test, in this the fabric is firmly fixed to the top half of the shear box and a standard laboratory soil is used in the bottom half.

The force required to cause sliding b/w the fabric & soil is determined for different normal stresses and the shear strength parameters are obtained.

This test is not a suitable test for assessing the parameters to be used for the analysis for reinforced soil. for reinforced soil application the proposed fill material should be used in the test.

Hydraulic properties:

water permeability of geotextile (permittivity method):

This test measures the quantity of water which can pass through a geotextile. The permeability may be measured either in a constant head or falling head method.

Constant head method is more common due to the high flow rates through geotextiles.

Since there are geotextiles of various thicknesses available it is better to evaluate them in terms of permittivity, which ~~measures~~ ^{indicates} the quantity of water passing

rough a geotextile under a given head over a particular area.

This test is useful in classifying geotextiles & for comparing the in isolation water permeability of geotextiles.

Instant head hydraulic transmissivity: This method may be used to estimate the in plane permeability of a geotextile or a Composite drain. The Sample is Confined, at varying normal stresses and the flow under a constant head is measured.

This test is useful for classifying geotextiles and geocomposite drains & will provide information to allow comparisons of in plane permeability to be made.

International testing standards for geotextiles.

- BS - British Standards
- EN - European Norms.
- ISO - International Standards organisation.
- ASTM - American Society of testing materials.

all provide testing methods for geotextiles & related products.

British standards:

- BS 6906 : part 1: 1987
wide width tensile test
[BSENISO 10319, ASTM D4585: 1988]
- BS 6906 : part 2: 1989
Determination of apparent pore size
distribution by dry sieving.
[ISO 12 956, ASTM D4951: 1993]
- BS 6906 : part 3: 1989
Determination of water flow normal to
the plane of geotextiles under a constant
head [ISO 11058, ASTM D4491: 1992]
- BS 6906 : part 4 : 1987
static pressure test (CBR)
[BSENISO 12236, ASTM D 4833: 1988]
- BS 6906 : part 5 : 1991
Determination of Creep (ISO 13341,
ASTM D5262: 1992)
- BS 6906 : part 7 : 1990
Determination of in plane waterflow.
[ISO 12958, ASTM D4416: 1987]
- BS 6906 : part 6 : 1990
Dynamic perforation test.
[BSEN 198, ISO 13 433, ASTM D4833:
1988]
- BS 6906 : part 8 : 1991
Determination of sand geotextile
frictional behaviour by direct shear
[ISO 12957 part 1, ASTM D4886: 1988]

American Society of testing materials:

ASTM D 3786: 1987: hydraulic bursting strength of knitted goods & nonwoven fabrics.

ASTM D4354: 1989: Sampling and preparation of test specimens (BSEN963, ISO 9862:1990)


ASTM D4491: 1992: determination of water flow normal to the plane of geotextile under a constant head (ISO 11058, BS 6906: part 3: 1989).

Geogrid: A geosynthetic material consisting of connected parallel set of intersecting ribs with apertures of sufficient size to allow strike through of surrounding soil, stone, or other geotechnical materials.

Thus geogrids are matrix like materials with large openings called apertures, which are typically 10 to 100mm b/w ribs that are called longitudinal & transverse respectively.

The ribs themselves can be manufactured from a ~~number~~ number of different materials, and the ribs cross-over joinings (or) junction bonding methods can vary.

The primary function of geogrids is clearly Reinforcement:

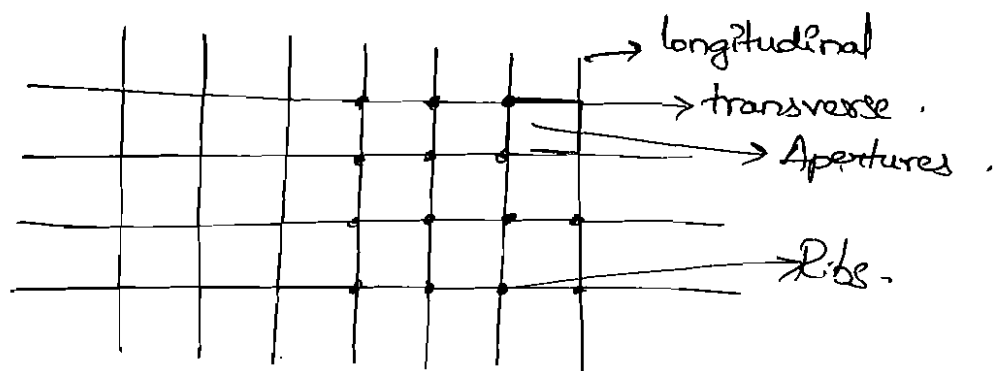

types: Axial & Braxial

properties: ① Geogrid tests are unique in a number of aspects when compared with geotextiles.

② properties relating to Separation, filtration,

drainage, and barrier, applications are not included since geogrids always serve the primary function of reinforcement.

Physical properties:

Many of the physical properties of geogrids - including the type of structure, sub dimensions, junction type, aperture ^{size} and thickness can be measured directly and are relatively straightforward.

Other properties like ① mass/unit area varies over a tremendous range from 200 to 1000 g/m².

② % open area which varies from 40 to 95%.

Density: ① The density (or) specific gravity of a geogrid depends upon the polymer from which it is made.

② Homogeneous geogrids are made from HDPE (or) PP and density can be measured using ASTM D792 (or) DISOS codes. & values obtained will be < 1 .

③ Rod (or) Strap geogrids made from PET can use the same test methods and the resulting value will be > 1 .

(2)
out of plane bending Stiffness: This test (Bending Stiffness) can be measured using ASTM D1388, a test for flexural rigidity. This test method slides a geogrid test specimen hanging over an inclined plane measuring an angle of 41.5° with the horizontal. When the geogrid bends and eventually touches the surface of the inclined plane, its distance is measured and then related to the mass/unit area.

The Strap geogrids are quite stiff and are characterized by having flexural rigidity values $>1000 \text{ g-cm}$.


The woven or knit yarn geogrids are quite ~~flexible~~ flexible and are characterized by having ~~flexural~~ flexural rigidity value less than ($<$) 1000 g-cm .

In this test.

In plane torsional Stiffness: In this test a bidirectional geogrid test specimen is clamped in a rigid frame and firmly gripping the central node.

A torque is applied and the angular rotation versus the geogrid resistance is measured.

The resulting plot shows a near linear performance for the stiff geogrids

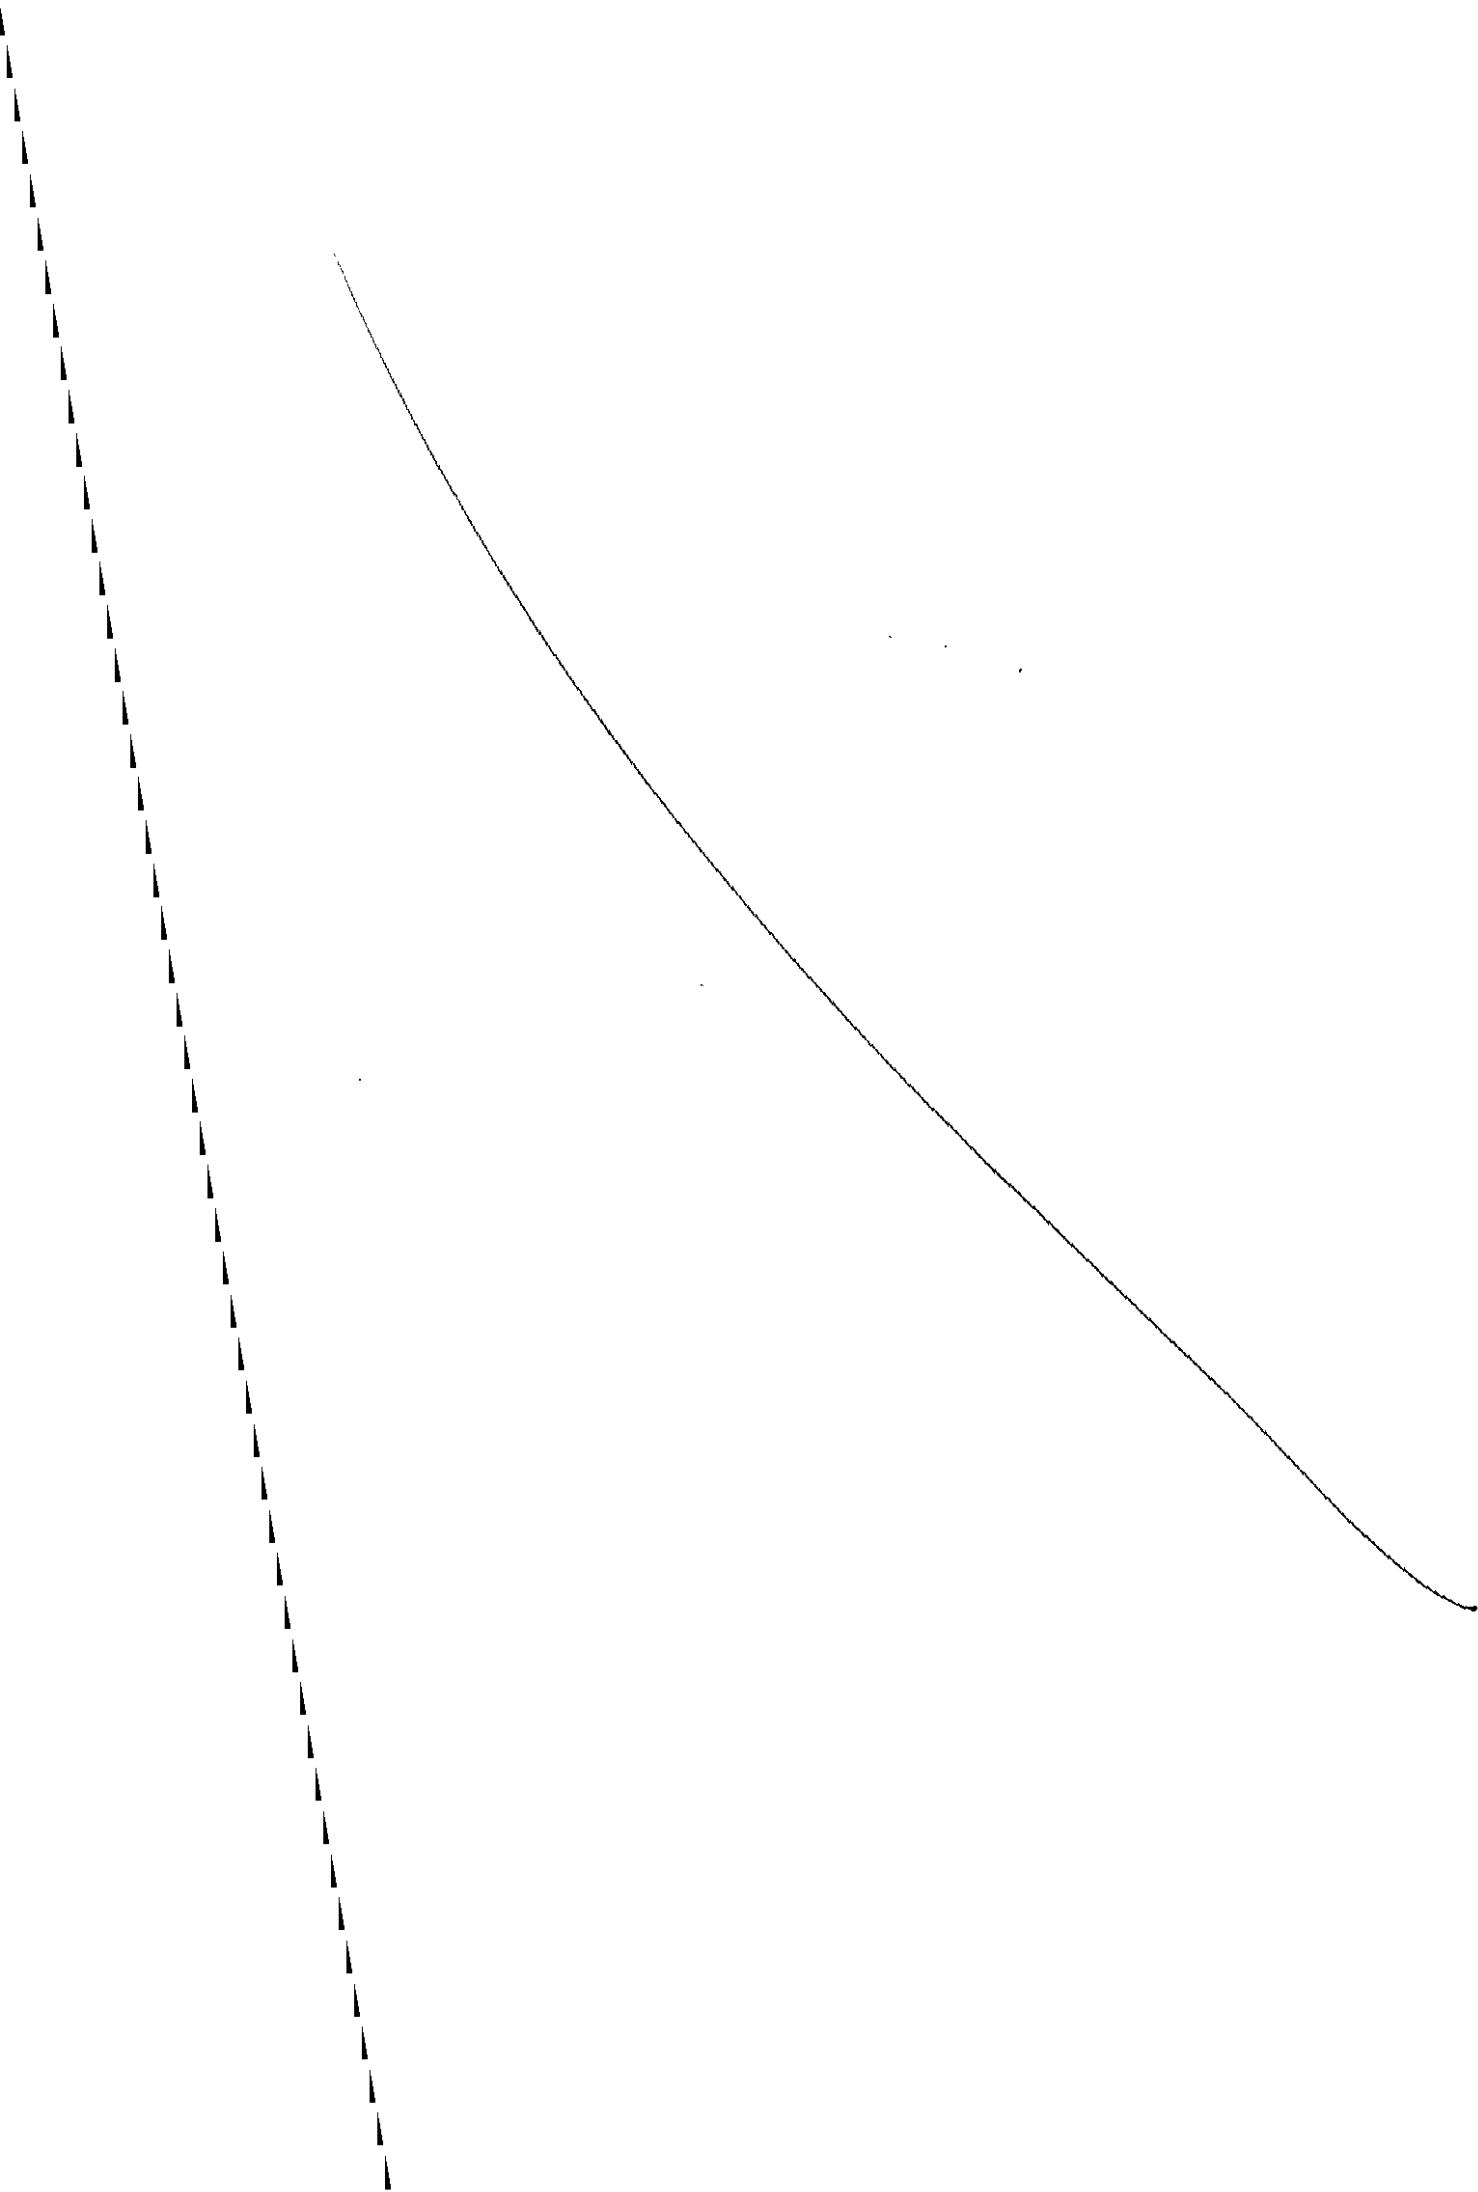

for the flexible geogrids the response is initially low, but after 5 to 10° rotation, the resisting force increases

This test is applicable for bidirectional geogrid reinforcement in pavement base courses & soil foundation stabilizations.

Mechanical properties:

wide width tensile strength: geogrid is clamped to a testing plate. Clearly the wide width tensile strength of a geogrid, in its machine direction for unidirectional geogrids and in both machine and cross machine directions for bidirectional geogrids. The resulting data gives strength of a geogrids in units of force per unit width, which is calculated by using the repeat distance of actual geogrid structure.

Obviously there is an extremely wide range in product behaviour, depending on type of polymer, its structure, spacing of ribs, and so on.

There are 2 procedural test methods used to evaluate the wide width tensile strength of geogrids. One choice is to use ASTM D6637.

which has a provision for measuring single rib strength or multiple rib strength.

Shear Strength: The geogrid is fixed to a block and is forced to slide over stationary soil in a shear box while being subjected to normal stress. The maximum shear stress, its shear strength is obtained. Then a new test with a replicate geogrid specimen and soil is conducted. This process is repeated sufficiently often to develop a set of shear strength versus normal stress points.

ENDURANCE properties:

Installation damage: geogrids undergo damage during the construction process.

→ The amount of damage depends upon the type of aggregate, level of compaction, type of compaction equipment & construction practices.

→ The installation damage factor is specified after extensile field test for site specific.

Conditions :

→ ASTM 5818 recommends that the results from at least 20 tests should be used to determine the installation damage factor.

typical damage factors are

- ① for use in gravels / aggregates 1.1 to 1.2 .
- ② for use in fine soils 1.05 to 1.1
- ③ for use in railway tracks the damage factor could be much higher because of the larger angular ~~practic~~ particles .

Tension Creep behavior: A major endurance property involving geogrids is their sustained - load deformation or tension "Creep". Since all polymers used in the manufacturing of geogrids consists of long-chains molecules arranged in crystalline regions with interspersed amorphous regions, the creep response reflects upon the percent crystallinity and the glass transition temperature.

Creep Rupture Behavior: A variation of the Tension Creep test just described is the Creep rupture ~~proed~~ procedure presented ~~by~~ by Ingold. In this procedure higher stresses are imposed on the test specimens, causing failure to occur in a relatively short time. Upon performing a number of such test, a graph of load - versus - log time can be generated. When extrapolated out to the desired service lifetime an acceptable load can be obtained. When normalized to the short term value, the inverse of this ratio becomes the reduction factor to be applied on ultimate strength.

21/9/17:

2, 5, 6, 9, 10, 14, 19, 21, 23, 24, 25, 26, 27, 30, 33, 35, 38, 39, 40, 41, 42, 43, 44, 47, 48, 49, 50, 54, 55. L-2, 4, 7, 8, 11, R-150.